

**Synthesis of GAP and PAMMO homopolymers from mesylate polymeric precursors**

Journal:	<i>Journal of Energetic Materials</i>
Manuscript ID:	UEGM-2015-1356.R2
Manuscript Type:	Original Article
Date Submitted by the Author:	n/a
Complete List of Authors:	Mura, Claudio; University of Pisa, civil and industrial engineering Fruci, Stefania; University of Pisa, civil and industrial engineering Lamia, Pietro; University of Pisa, civil and industrial engineering Cappello, Miriam; University of Pisa, civil and industrial engineering Filippi, Sara; University of Pisa, civil and industrial engineering Polacco, Giovanni; University of Pisa, civil and industrial engineering
Keywords:	Binder, Azides, GAP, AMMO, mesyl

SCHOLARONE™  
Manuscripts

**Synthesis of GAP and PAMMO homopolymers from mesylate polymeric precursors**Short title: **Azidic binders from mesylate precursors**

Claudio Mura, Stefania Fruci, Pietro Lamia, Miriam Cappello, Sara Filippi, Giovanni Polacco \*

*Department of Civil and Industrial Engineering*

*University of Pisa*

*Largo Lucio Lazzarino, 2 – 56126 Pisa, ITALY*

\* Corresponding author

e-mail: [giovanni.polacco@unipi.it](mailto:giovanni.polacco@unipi.it)

phone: +39 050 2217820

fax: +39 050 2217866

**Abstract**

In azidic binders for solid propellants, the N<sub>3</sub> functionality is introduced by substitution of a halogen or tosyl group, but recently the mesyl group has been suggested as an alternative. The mesylate group has two advantages, mainly related to its small dimension and low cost. Poly(glycidyl azide) and poly 3-azidomethyl-3-methyl oxetane were prepared by using both tosylate and mesylate precursors. The azidation kinetics were studied at three different temperatures while keeping equal all the other operating parameters. The results confirmed the good potential of the mesylate precursors for the production of azidic binders.

## 1. Introduction

In solid propellant formulations, a reducer and an oxidizer in form of dry powder are mixed with a liquid pre-polymer that allows the formulation to be cast into large and irregular cases [1]. The polymer is then cross-linked to form an elastomeric network that provides mechanical integrity and safety during storage and transportation [2]. The most commonly used binder is hydroxy-terminated polybutadiene (HTPB), which, after cross-linking with isocyanates, provides optimal mechanical properties. However, HTPB do not contributes to the overall energy output and therefore the research is focused on alternative binders that could improve the propellant performance. During the last decades, several energetic binders have been developed and the interested reader may find detailed information in the reviews by Agrawal [3], Provatas [2], Badgular et al. [4], Sikder and Sikder [5] and Gaur et al. [6].

Among the proposed binders, polyethers containing azidic functionalities are very promising and glycidyl azide polymer (GAP) is the most studied one. Several publications may be found concerning the synthesis as well as the thermal behavior and explosive properties of GAP [7-22]. The GAP synthesis was first described in a patent filed in 1972 by Vandenburg [23] who did azidation of polyepichlorohydrin (PECH) by using sodium azide in dimethylformamide. Twenty years later, Frankel et al. described a semi-industrial production of GAP in USA [24]. Other suggested polymeric azides are poly(3,3 bis(azidomethyl)oxetane-co- $\epsilon$ -caprolactone) [25], 3,3 bis(azidomethyl)oxetane-tetrahydrofuran [26, 27], polyglycidylazide-*b*-poly(azidoethyl methacrylate) [28] and polyoxetanes [6, 29-35], first synthesised by Manser [36-38], such as 3-nitratomethyl-3-methyl oxetane (NIMMO), 3,3-bis-(azidomethyl)oxetane (BAMO) and its analog monofunctional 3-azidomethyl-3-methyl oxetane (AMMO). In the first synthesis, the chlorinated or tosylate monomer was azidated and then subjected to cationic ring-opening polymerization by using a diol and a Lewis acid as catalyst. The approach is now changed, since the azidated ring-monomers are highly dangerous and may

1  
2  
3 easily explode during processing and handling. Therefore, it is better if the azidation step  
4 follows the polymerization of non-energetic monomers [34]. This is a low technology, low-  
5 risk approach, but gives less opportunity to tailor the final properties of the polymer and  
6 suffers from the usual complications of modifying a macromolecule [39]. This means that  
7 azidation became the critical step: it may be time demanding and often does not proceed to  
8 complete substitution of the functional groups into azidic ones. Sodium azide is the preferred  
9 reagent for azidation, which has been performed in several organic solvents as well as in  
10 water [24, 40]. A procedure involving molten azidic salts has also been described [41]. In the  
11 first case, the reaction is much faster and proceeds in a homogeneous reaction medium, while  
12 in water, the use of a phase transfer catalyst is necessary.

13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25 The research in the synthesis of azidated polyethers is therefore mainly focused on both the  
26 tailoring of the binder properties and, in view of the industrial process, the optimization of the  
27 azidation step. The goal is to overcome the production difficulties and make the process  
28 competitive with that of HTPB, while keeping the advantages related to the higher energy  
29 input of the final product.

30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
The thermodynamics and kinetics of the azidation reaction depend on two main factors: the  
chemical nature of the leaving group and the operating conditions. With regard to the first  
point, many different functionalities may be used as leaving group to facilitate the introduction  
of the azidic group through a SN2 type mechanism. The most used ones are halogens, which  
however present a few disadvantages mainly related to the difficulty of obtaining their  
complete substitution that may require very long reaction times. Moreover, considering the  
well-known flame-retardant effect of halogens, it may be supposed that an incomplete  
substitution, could considerably limit the efficacy of the energetic binder. The tosyl group is  
an interesting alternative to halogens. This is a very good leaving group, but its steric  
hindrance may represent a problem. In other words, it may be difficult to remove the tosyl

1  
2  
3 group from a polymeric chain. This is because, even if the macromolecules are dissolved in a  
4  
5 solvent, the presence of many neighboring tosyl groups may considerably limit the access of  
6  
7  $N_3$  groups to the reactive site and thus also the overall kinetic of azidation. This problem has  
8  
9 been recently discussed by Cappello et al. [42] with respect to the synthesis of ether-HTPB-  
10  
11 ether tri-block copolymers. Moreover, the steric hindrance may also play a role during  
12  
13 polymerization and influence i.e. the molecular weight of the polymeric precursor.

14  
15  
16 With regard to the operating conditions, these include the appropriate choice of the solvent (or  
17  
18 mixture of solvents) and temperature. The solvent must be a good one for monomers and the  
19  
20 forming polymers and, of course, it has to solubilize at least partially the sodium azide.

21  
22  
23 Another important aspect is the solvent boiling point. Higher boiling points allow higher  
24  
25 reaction temperatures and thus shorter reaction times, but may complicate the purification of  
26  
27 the final product. Moreover, too high temperatures may lead to partial decomposition of the  
28  
29 azide groups [34]. Polymeric precursor and operating condition must be chosen in order to  
30  
31 balance and optimize the above-mentioned factors. A partial list of azidation conditions  
32  
33 described in the scientific and patent literature is reported in Table 1. DMF

34  
35 (dimethylformamide) and DMSO (dimethyl sulphoxide) are by far the preferred solvents.

36  
37  
38 To better understand the role of the leaving group in the synthesis of azidic binders, we  
39  
40 prepared two different polyethers starting from tosylate and mesylate precursors. While the  
41  
42 tosyl (Ts) group is well known and already adopted in the synthesis of energetic binders, the  
43  
44 mesyl (Ms) one has not yet been used in this field. Therefore, on one side we have a bulky  
45  
46 and heavy aromatic group, which is potentially one of the better leaving groups, while on the  
47  
48 other one there is a smaller and lighter functional group, theoretically less suitable for  
49  
50 azidation. The synthesized polymers are GAP and poly 3-azidomethyl-3-methyl oxetane  
51  
52 (PAMMO). Thus, we compared tosyl and mesyl groups with both oxirane and oxetane  
53  
54 starting monomers. This corresponds to four synthesis, as summarized in Figure 1. All the  
55  
56  
57  
58  
59  
60

1  
2  
3 monomers, polymeric precursors and azidic binders were characterized by Fourier-Transform  
4  
5 Infra-Red (FTIR) analysis and Nuclear Magnetic Resonance (NMR); the molecular weight of  
6  
7 the polymers were evaluated by Gel Permeation Chromatography (GPC); their thermal  
8  
9 behavior by Thermogravimetric Analysis (TGA). Moreover, the azidation reactions were  
10  
11 performed at different temperatures, with time/conversion curves obtained by FTIR and used  
12  
13 to evaluate the kinetic parameters.  
14  
15

## 16 17 18 **2. Materials and methods**

### 19 20 **2.1. Materials**

21  
22 All the chemicals, unless differently stated, were purchased from Sigma Aldrich. Toluene  
23  
24 (99,8%), dimethylformamide (DMF) (99.8%), methanol (99.9%), sodium azide (>99.5%),  
25  
26 boron trifluoride tetrahydrofuranate (BTF·THF), triethylamine (TEA) ( $\geq 99\%$ ), 3-hydroxy-  
27  
28 methyl-3-methyloxetane (HMMO) (98%), glycidol (G) (96%), toluene-4-sulfonyl chloride  
29  
30 (TsCl) ( $\geq 99\%$ ), methanesulfonyl chloride (MsCl) (>99.7), sodium chloride (>99%), sodium  
31  
32 hydroxide (>98%), sodium carbonate anhydrous (>99.7), magnesium sulfate (>99.5),  
33  
34 phosphorous pentoxide, hydrochloric acid, potassium hydroxide were used as received.  
35  
36 Diethyl-ether and dichloromethane (DCM) were dried with  $P_2O_5$  and distilled at 1 atm.  
37  
38 Epichlorohydrin (ECH) and butanediol (99.9%) (BDO) were distilled under the reduced  
39  
40 pressure.  
41  
42  
43  
44  
45  
46

### 47 48 **2.2. Synthesis of the monomers**

#### 49 50 **2.2.1. Glycidyl tosylate (GT)**

51  
52 The synthesis was performed according to a procedure described by Nakabayashi et al [46]. A  
53  
54 250 mL two-necked round bottom flask, fitted with a nitrogen inlet and a mechanical stirrer  
55  
56 set at 180 rpm was fed with 50 mL of anhydrous toluene and 4.2 mL of TEA (corresponding  
57  
58  
59  
60

1  
2  
3 to a G/TEA=1/1 molar ratio). In a beaker a solution of 5.42 g TsCl (corresponding to a  
4  
5 TsCl/G=0.95/1.0 molar ratio) in 12 mL of toluene was also prepared. The round bottom flask  
6  
7 and the beaker were then conditioned at -15°C for 1.5 h. At the end of conditioning time, the  
8  
9 round bottom flask was fed with 2 mL of distilled G (also cooled to -15°C) and then drop-  
10  
11 wise with the TsCl solution while maintaining the system under gentle stirring. At the end of  
12  
13 the TsCl feeding, the stirrer was stopped and the system maintained at -15 °C for 24 h. Then,  
14  
15 the solution was filtered under vacuum to remove the solid TEA·HCl complex and distilled at  
16  
17 65 °C and 2000 Pa to remove the toluene. The remaining liquid was dropped slowly into cold  
18  
19 petroleum-ether (containing a few GT crystals previously prepared with the same procedure,  
20  
21 in order to favor the crystallization process) thus forming a white suspension that crystallizes  
22  
23 while cooled at -15°C. The petroleum ether was finally removed by distillation under vacuum.  
24  
25 The GT was obtained with a 98.6% yield, as white anhydrous crystals.  
26  
27  
28  
29  
30  
31

### 32 2.2.2. Glycidyl mesylate (GM)

33  
34 The synthesis was performed according to a procedure described by Nakabayashi et al [46]. A  
35  
36 500 mL two-necked round bottom flask, fitted with a nitrogen inlet and a mechanical stirrer  
37  
38 set at 180 rpm was fed with 100 mL of anhydrous toluene and 22.2 mL of TEA. In a 250 mL  
39  
40 beaker a solution of 11.7 mL MsCl in 20 mL of toluene was also prepared. The round bottom  
41  
42 flask and the beaker were then conditioned at -15°C for 1.5 h. At the end of conditioning time,  
43  
44 the round bottom flask was fed with 11 mL of distilled G (also cooled to -15°C) and then  
45  
46 drop-wise with the MsCl solution while maintaining the system under gentle stirring. At the  
47  
48 end of the MsCl feeding, the stirrer was stopped and the system maintained at -15 °C for 24 h.  
49  
50 Then, the solution was filtered under vacuum and distilled at 65 °C and 2000 Pa to remove the  
51  
52 toluene and obtain GM as a yellowish liquid with a 84% yield.  
53  
54  
55  
56  
57  
58  
59  
60

### 2.2.3. 3-tosyloxymethyl-3-methyl oxetane (TMMO)

The synthesis was performed in the solid state, according to a procedure described by Kazemi et al [47]. A mortar was fed with 31.8 g of anhydrous  $\text{Na}_2\text{CO}_3$ , 10.2 g of HMMO ( $\text{Na}_2\text{CO}_3/\text{HMMO}=3/1$  molar ratio) and manually milled with a pestle for about 7 min. Then 28.7 g of TsCl ( $\text{TsCl}/\text{HMMO}=1.5/1$  molar ratio) were added and milled for further 23 min. Finally, 28.05 g of KOH were added ( $\text{KOH}/\text{HMMO}=5/1$  molar ratio) and milled for about 50 min to remove the unreacted TsCl. The whole reaction was conducted in a glove box under nitrogen atmosphere. The obtained solid was added to 200 mL of diethyl-ether and filtered several times. The obtained clear liquid phase was finally subjected to distillation at  $48^\circ\text{C}$  and 8500 Pa thus inducing the crystallization of TMMO that was obtained with a 40 % yield.

### 2.2.4 3-mesyloxymethyl-3-methyl oxetane (MMMO)

The synthesis was performed according to a procedure described by Nakabayashi et al [46]. A 500 mL two-necked round bottom flask, fitted with a nitrogen inlet and a mechanical stirrer set at 180 rpm was fed with 150 mL of anhydrous toluene and 13.7 mL of TEA. In a 250 mL beaker, a solution of 7.22 mL MsCl in 30 mL of toluene was also prepared. The round bottom flask and the beaker were then conditioned at  $-15^\circ\text{C}$  for 1.5 h. At the end of conditioning time, the round bottom flask was fed with 10 mL of distilled HMMO (also cooled to  $-15^\circ\text{C}$ ) and then drop-wise with the MsCl solution while maintaining the system under gentle stirring. At the end of the MsCl feeding, the stirrer was stopped and the system maintained at  $4^\circ\text{C}$  for 24 h and distilled at  $65^\circ\text{C}$  and 2000 Pa to remove the toluene. The remaining liquid was then placed in a fridge to crystallize and recover the MMMO.

## 2.3. Polymerizations



1  
2  
3 The polymerization may proceed either by: the Active Chain End (ACE) mechanism, or the  
4  
5 Activated Monomer Mechanism (AMM). The first one involves protonation of the oxetane  
6  
7 and subsequent propagation until the chain is terminated either with water or alcohol to give  
8  
9 the hydroxy-terminated polymer. ACE allows a reasonable molecular weight control, but may  
10  
11 lead to the formation of cyclic oligomers [39]. In AMM, which has considerable similarities  
12  
13 with the living polymerization, the growing chain is OH terminated and the “active” role is  
14  
15 played by the monomer. In this case the side reactions, including cyclization, should be  
16  
17 minimized [6]. However, it must be underlined that it is not easy to drive the reaction toward  
18  
19 the desired mechanism and often both mechanisms may be present at the same time [31, 35].  
20  
21 For our synthesis, the catalyst and operating conditions were set in order to favor the AMM.  
22  
23 BTF·THF and butanediol were used to initiate the polymerization and the quantities were  
24  
25 chosen to have a molar ratio between BTF·THF and OH functionalities equal to 2/1, while the  
26  
27 molar ratio between monomers and OH functionalities was equal to 50/1. The polymerization  
28  
29 procedure was as follows. A 1L three-necked round bottom flask, fitted with a reflux  
30  
31 condenser, a nitrogen inlet and a mechanical stirrer set at 120 rpm was fed with 80 ml of  
32  
33 DCM, 0.15 mL of BTF·THF, about 0.031 g of BDO and maintained for 2 h under stirring at  
34  
35 room temperature. Then, the reactor was covered with aluminum foil, immersed in a water  
36  
37 bath at  $20 \pm 0.5$  °C and the monomer (0.0345 mole), previously dissolved in 30 mL of DCM,  
38  
39 was added drop-wise to the reactor through a dropping funnel. From the end of the monomer  
40  
41 feeding, the reaction mixture was kept in the same conditions for 20 or 120 h (mesylate or  
42  
43 tosylate monomers respectively) and then hydrolyzed with 400 mL of an aqueous solution of  
44  
45 NaCl (10% w). The mixture was maintained under vigorous stirring for further 2 h and then  
46  
47 the organic and aqueous phase were separated. The aqueous phase was washed with DCM,  
48  
49 subsequently recovered and added to the organic phase. The organic phase was washed once  
50  
51 with a water/methanol = 50/50 v/v solution to remove unreacted monomers and catalyst, then  
52  
53  
54  
55  
56  
57  
58  
59  
60

again several times with the aqueous solution of NaCl, dried with MgSO<sub>4</sub>, filtered and distilled at 45 °C, under vacuum (6500 Pa) in order to remove all the DCM.

#### 2.4 Azidation

The azidation is a second-order reaction with SN<sub>2</sub> type mechanism performed using sodium azide in DMF. As already underlined (see Table 1) these azidation conditions are well known and have been already used by our research group [30, 31, 33-35].

A typical azidation procedure was as follows. About 2 g of polymeric precursor were dissolved in 100 ml of DMF and fed in a 250 mL three-necked round bottom flask, fitted with a reflux condenser, a nitrogen inlet and a magnetic stirrer. The flask was immersed in an oil bath set at 85±1 °C and conditioned for 30 minutes. Then, NaN<sub>3</sub> was added in 20% molar excess with respect to the stoichiometric quantity and the temperature of the bath raised to the desired temperature while maintaining the system under constant stirring. Periodically, samples were taken from the reactor and subjected to FTIR analysis to evaluate the degree of azidation. Once the IR spectra were stationary, the reaction medium was filtered under vacuum in order to remove the formed sodium salts and the unreacted sodium azide.

The solution was then washed several times with an aqueous solution of NaCl (10 % w) in order to complete the salts removal. The aqueous phases resulting from the washings were mixed together and washed with DCM to remove possible traces of polymer, while the organic phase was dried with MgSO<sub>4</sub>, filtered again and distilled at 45 °C, under vacuum (1000 Pa) in order to remove all the organic solvents.

The structure and purity of all synthesized polymers (before and after azidation) were checked by FTIR and NMR, while their thermal properties were determined by TGA.

#### 2.5. Characterization of the monomers and polymers

1  
2  
3 Fourier-transform infrared spectroscopy was performed on a Bruker Tensor 27 and nuclear  
4 magnetic resonance ( $^1\text{H-NMR}$ ,  $^{13}\text{C-NMR}$ ) on a VXR300 and INOVA600 instruments.

5  
6  
7 Thermogravimetric analysis was done by using a TA Q500 apparatus, under nitrogen  
8 atmosphere, with a heating rate of  $10^\circ\text{C}/\text{min}$  until  $600^\circ\text{C}$  and using samples of about 5 mg.

9  
10 The molecular weight of the polymers was measured from solution in  $\text{CHCl}_3$  (2 mg/mL) by  
11 using a Gel Permeation Chromatography (GPC) apparatus Jasco PU-1580, equipped with PL  
12 Mesopore column, calibrated with low polydispersity polystyrene standards.  
13  
14  
15  
16  
17  
18  
19

### 20 21 **3. Results and discussion**

#### 22 23 3.1. Chemical characterization (IR – NMR)

24  
25 The FTIR spectra of all monomers and polymers are reported in Figure 2. The main peaks  
26 corresponding to the tosyl, mesyl and azidic functionalities are:  $1174\text{-}1176\text{ cm}^{-1} = \nu_s \text{SO}_2$ ,  
27  
28  $1280\text{ cm}^{-1} = \nu_s \text{N}_3$ ,  $1350\text{-}1360\text{ cm}^{-1} = \nu_{as} \text{SO}_2$ ,  $1600\text{ cm}^{-1} = \nu \text{C}=\text{C}$  aromatic ring,  $2100\text{ cm}^{-1} =$   
29  
30  $\nu_{as} \text{N}_3$ . Some of these peaks have been chosen for the kinetics study, as reported in section  
31  
32  
33  
34  
35 3.3.

36  
37 For the sake of brevity, the NMR spectra are reported only for the mesylate compounds  
38 (Figure 3), which are not common in the binder literature. Nevertheless, all the NMR spectra  
39 were recorded and confirmed the chemical composition and high purity of the synthesized  
40 compounds. Moreover, the NMR spectra were useful to confirm the absence of tosyl or mesyl  
41 groups in the energetic polymers, so that a final conversion equal to 1 was assumed for the  
42  
43  
44  
45  
46  
47  
48 azidation reactions.  
49

#### 50 51 52 3.2. Molecular weights

53  
54 The GPC analysis was performed on the polymeric precursors. As an example, Figure 4  
55 shows the spectrum of PGT (a) and the corresponding fit after deconvolution into two  
56  
57  
58  
59  
60

1  
2  
3 separate peaks (b). The spectra of the other polymeric precursors are qualitatively similar and  
4  
5 in all cases showed a small peak corresponding to the formation of oligomers. A  
6  
7 deconvolution procedure was then used to calculate separately the mean average molecular  
8  
9 weights of polymer and oligomers.  
10

11 Table 2 reports the number ( $M_n$ ) and weight ( $M_w$ ) average molecular weights, the average  
12  
13 degree of polymerization ( $X_n = M_n/M_0$ , where  $M_0$  is the molecular weight of the repeating  
14  
15 unit) as well as the polymer dispersion ( $PD = M_w/M_n$ ) and the  $X_n$  and weight fraction of the  
16  
17 oligomers. A first observation was that the molecular weights were relatively low. The higher  
18  
19  $X_n$  was found for the case of PMMO and it is about half that of the HTPB used as binder for  
20  
21 propellants. However, it should be emphasized that the operating conditions were fixed a  
22  
23 priori and then applied to all polymerizations. The molecular weight optimization was not an  
24  
25 objective of this work and may be modulated by changing many operating parameters as  
26  
27 temperature, BDO concentration, catalyst, solvent etc. Nevertheless, these values are  
28  
29 comparable with previous results reported for energetic binders (see e.g. [30]). Another  
30  
31 interesting point is that in both cases the mesylate monomers gave longer polymeric chains.  
32  
33 Since the four polymerization reactors were fed with the same monomer/initiator ratio and  
34  
35 molar concentrations, in case of similar yield the polymers should also have similar  $X_n$ .  
36  
37 Therefore, the  $X_n$  values can be somehow read as an indicator of the reaction yield.  
38  
39  
40  
41  
42  
43  
44

### 45 3.3. Azidation kinetics

46  
47 In order to quantify the azidation kinetics of the four polymeric precursors, the time-  
48  
49 conversion curves were obtained at three different temperatures. For each precursor, the  
50  
51 temperatures were chosen in order to obtain reasonable reaction times. A too fast reaction  
52  
53 strongly complicates the sampling procedure and may induce errors in the estimation of the  
54  
55 time-conversion curve. A too slow reaction is not advisable for future potentially large scale  
56  
57  
58  
59  
60

1  
2  
3 productions. As described in section 2.4., samples were taken from the reaction medium at  
4  
5 different times and their IR spectra recorded and analyzed. Of course, the peaks available to  
6  
7 follow the azidation are those corresponding to both the incoming  $N_3$  and the leaving tosyl or  
8  
9 mesyl groups. The  $N_3$  asymmetric stretching at  $2100\text{ cm}^{-1}$  was chosen among the  $N_3$  peaks  
10  
11 because it falls on a clean zone (for both azidated polymers), where it can be easily detected  
12  
13 and integrated. This peak has the disadvantage that it tends to increase in intensity at low  
14  
15 conversion and broaden at high conversions. This may lead to a partial superposition with the  
16  
17  $CO_2$  peak, which never completely disappears even though the base line was recorded and  
18  
19 subtracted each time. As a consequence, the integration was a bit noisy at high conversions.  
20  
21 With regard to the tosyl and mesyl groups, the symmetric stretching of  $SO_2$  at  $1174\text{-}1176\text{ cm}^{-1}$   
22  
23 was chosen. In this case the disadvantage is that the peaks are in the fingerprint region, where  
24  
25 1) the superposition with neighbor peaks may happen and 2) it may be difficult to recognize  
26  
27 the base line.  
28  
29

30  
31 In order to find the best way to evaluate the peak area, we compared the data obtained with or  
32  
33 without a deconvolution analysis of the peaks and we did not found significant differences  
34  
35 between the two procedures. The presence of the above-mentioned uncertainties (peak  
36  
37 overlapping, ambiguous base line) is the reason why the time-conversion curves were  
38  
39 evaluated by using both  $N_3$  and tosyl (mesyl) peaks: since the azidic one substituted the tosyl  
40  
41 (mesyl) groups, the two conversions are supposed to coincide and can be used to crosscheck  
42  
43 one each other. As the reference peak, the  $CH_2$  scissoring at  $1456\text{ cm}^{-1}$  was chosen (see Figure  
44  
45 2).  
46  
47

48  
49 As an example, Figure 5 show the time dependence of the FT-IR spectra during azidation of  
50  
51 PGM at  $85\text{ }^\circ\text{C}$ .  
52

53  
54 Since the NMR analysis of the final products in all cases indicated a complete azidation, the  
55  
56 conversions were evaluated as:  
57  
58  
59  
60

$$x_{N(t)} = \frac{A_N(t)/A_N(t_f)}{A_R(t)/A_R(t_f)} \quad (1)$$

$$x_{T(t)} = 1 - \frac{A_T(t)/A_T(t_0)}{A_R(t)/A_R(t_0)} \quad (2)$$

$$x_{M(t)} = 1 - \frac{A_M(t)/A_M(t_0)}{A_R(t)/A_R(t_0)} \quad (3)$$

where the N, R, T, M subscripts indicate azide, reference, tosyl and mesyl groups respectively,  $t$  is time,  $t_0$  and  $t_f$  are start and end of the reaction and A indicates the area of the peak (evaluated in absorbance and expressed in arbitrary units).

All azidations were performed with a starting quantity of sodium azide corresponding to a 20% excess with respect to the stoichiometry. In the chosen operating conditions, the sodium azide fed to the reactor corresponds to a quantity lower than its solubility limits. Assuming that the substitution is an elementary reaction, we have a second order kinetic law. Moreover, if we disregard volume changes, the following kinetic expression can be written [34]:

$$v = \frac{d[N_3]}{dt} = -\frac{d[T]}{dt} = -k[N_3][T] \quad (4)$$

where  $v$  is the reaction rate,  $[T]$  and  $[N_3]$  are the concentrations of unreacted tosyl and azido groups, respectively,  $t$  is the time and  $k$  the kinetic constant. Of course, equation (4) is valid also for the mesyl precursor, simply substituting  $[T]$  with  $[M]$  = concentration of the mesyl groups. Since:

$$[N_3]_0 - [N_3]_t = [T]_t - [T]_0 \quad (5)$$

where the subscripts refer to time. Equation (5) has solution:

$$[T] = \frac{(r-1)[T]_0}{r \exp[kt[T]_0(r-1)]-1} \quad (6)$$

where  $r = [N_3]_0/[T]_0 = 1.2$ . Equation (6) can be also written as:

$$x_T = \frac{\exp[kt[T]_0(r-1)]-1}{\exp[kt[T]_0(r-1)]-1/r} \quad (7)$$

Again, the same equation applies to the azidic and mesyl functionalities, therefore equation (7) can be “generalized” simply including the initial concentration in the kinetic constant:

$k' = k[T]_0$ :

$$x = x_T = x_N = x_M = \frac{\exp[k't(r-1)]-1}{\exp[k't(r-1)]-1/r} \quad (8)$$

Equation (8) can be used to fit the experimental data of  $x_T$ ,  $x_S$  and  $x_N$  and obtain an estimation of  $k'$ .

As already underlined, the experimental time-conversion curves were obtained for each reaction by using both the azide and mesyl (or tosyl) signals from the FTIR spectra. These values should theoretically coincide, but of course the inevitable uncertainties correlated with the use of IR spectra for quantitative analysis lead to small discrepancies. As an example, the

1  
2  
3 comparison of conversion obtained with azide and mesyl signals in the case of PGM at 85°C  
4  
5 is reported in Figure 6. The image clearly shows that  $x_N$  has an irregular trend between 30 and  
6  
7 60 minutes, while  $x_M$  gives a more reliable and smooth behavior. Nevertheless, the two sets of  
8  
9 data are in good accordance and the reported example was chosen because it is the one where  
10  
11 the noise in  $x_N$  is more pronounced.  
12

13  
14 As a second example, the PMMMO azidation kinetics at different temperatures, obtained  
15  
16 from the mesyl peaks, are reported in Figure 7, together with the best fit obtained from  
17  
18 equation (8) with  $k'$  as unique fitting parameter. The whole list of estimated  $k'$  values for the  
19  
20 four polymers is reported in Table 3, together with the activation energy ( $E_a$ ) and the pre-  
21  
22 exponential factor ( $A$ ) evaluated by a linear fit in the plot of the logarithmic  $k'$  values against  
23  
24 the inverse of temperature, expressed in Kelvin degrees.  
25  
26

27  
28 Independently on the use of mesyl or tosyl groups, the azidation reaction was faster for GAP  
29  
30 than for PAMMO. This is why in the first case the adopted temperatures were 75, 85, and 95  
31  
32 °C, while they were raised to 85, 105 and 125 for PAMMO. As expected, in both cases the  
33  
34 temperature strongly influences the rate of reaction and the time needed for a quantitative  
35  
36 azidation may vary from approximately one week to about one day while comparing the  
37  
38 lower and higher tested temperatures. The  $k'$  values reported in Table 3 confirms that the tosyl  
39  
40 group is a better leaving group in the case of GAP precursors. In contrast, in the case of  
41  
42 PAMMO the difference between the two precursors is less pronounced and the mesyl group is  
43  
44 the one with the highest azidation kinetic. Moreover, it is interesting to observe that for both  
45  
46 polymers the azidation reaction from the mesylate precursors has a higher activation energy  
47  
48 (thus indicating a higher dependence on temperature) and a higher pre-exponential factor  
49  
50 (thus indicating a higher frequency of collisions between reactant molecules). A simple  
51  
52 theoretical calculation indicates that in the case of GAP the azidation kinetics from the two  
53  
54 different precursors should coincide at about 110 °C which is still in a feasible range of  
55  
56  
57  
58  
59  
60



1  
2  
3 operating temperature (even lower than those already adopted for PAMMO in the present  
4  
5 study).

6  
7 Finally, it is interesting to report the thermogravimetric analysis of the polymers and  
8  
9 corresponding precursors (Figure 8). As it has been already observed and discussed in many  
10  
11 other works, the azidic polymers shows a two-step decomposition behaviour [7, 11, 16, 21,  
12  
13 48]. The nitrogen release from the  $N_3$  group is responsible for the first step, while during the  
14  
15 second step the main chain decomposition occurs. It is not the aim of this work to discuss this  
16  
17 well-known behaviour, which has been already showed for both GAP and PAMMO  
18  
19 polymers. The curves presented here because they allow the comparison between behavior of  
20  
21 polymers prepared from tosyl and mesyl precursors. It can be clearly seen that the thermal  
22  
23 behaviour of the azidated polymers are almost identical, with the differences comparable to  
24  
25 the experimental uncertainty always present while observing fast and uncontrollable  
26  
27 decomposition phenomena.  
28  
29  
30  
31  
32  
33

#### 34 **4. Conclusions**

35  
36 Azidic binders are probably the most interesting and promising alternative to HTPB and the  
37  
38 scientific research was focused on their synthesis for many years. Usually, the  $N_3$   
39  
40 functionality is added to a polymeric precursor by  $SN_2$  type substitution of a halogen or tosyl  
41  
42 group. The use of chlorine and bromine, as groups have some disadvantages, mainly related  
43  
44 to the possibility of incomplete substitution during azidation. The residual halogen atoms may  
45  
46 impart a sort of anti-flame character to the binder and significantly reduce its efficiency.  
47  
48

49 Analogously, the tosyl group has disadvantages related to its very high molecular weight,  
50  
51 which strongly increases the weight of reagents and by-product to be processed. This is  
52  
53 negligible on the lab scale, but may represent a problem to scale up the process for industrial  
54  
55 production. Moreover, the introduction of several tosyl groups in a polymeric chain may  
56  
57  
58  
59  
60

1  
2  
3 result in a steric hindrance that can limit both the molecular weight of the polymer and its  
4  
5 reactivity during azidation. This is the reason why the methane-sulfonyl chloride has been  
6  
7 suggested as a potential alternative to halogen and tosyl groups. On a theoretical basis, the  
8  
9 mesyl group should be comparable to the tosyl one in leaving the polymeric chain during  
10  
11 azidation. However, there are also some potential advantages connected with the use of such  
12  
13 molecule. First of all, it is convenient from an economic point of view, since it is a low cost  
14  
15 compound that can be easily introduced in the oxetane and oxirane monomers. Secondly, the  
16  
17 reduced dimension, when compared to the tosyl group, allows a greater mobility of the  
18  
19 polymeric chains. The synthesis and azidation of GAP and PAMMO starting from tosyl and  
20  
21 mesyl precursors confirmed the high potential of the latter. The mesylate precursors were  
22  
23 prepared in form of oxetanic and oxiranic monomers, subsequently polymerized and azidated.  
24  
25 From the operating point of view, all the synthetic steps were comparable with those adopted  
26  
27 for the case of conventional precursors. The azidation reaction led to fully substituted  
28  
29 polymers, with final properties almost identical to those prepared by using the tosyl groups.  
30  
31 Finally, the kinetic of azidation at high temperatures showed to be perfectly comparable with  
32  
33 that of the other precursors. This is not surprising if we consider that: 1) the tosyl  
34  
35 functionality, as a better (more stable) leaving group, simply lowers the transition state  
36  
37 energy, relative to that of the mesyl analogue; 2) the higher mobility of the mesyl groups  
38  
39 leads to a pre-exponential factor two or three order of magnitude higher than that of the  
40  
41 tosylated reactant. We can thus conclude that methane-sulfonyl (mesyl) group is a good  
42  
43 candidate for the production of azidic binders for solid rocket propellants.  
44  
45  
46  
47  
48  
49  
50

## 51 **5. References**

52  
53  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3 [1] Colclough, M. E., H. Desai, R. W. Millar, N. C. Paul, M. J. Stewart, and P. Golding.  
4  
5 1993. Energetic polymers as binders in composite propellants and explosives. *Polymers for*  
6  
7 *Advanced Technologies*, 5:554-560.  
8
- 9 [2] Provatas, A. 2000. Energetic polymers and plasticisers for explosive formulations - A  
10  
11 review of recent advances, DSTO-TR-0966.  
12
- 13 [3] Agrawal, J. P. 1998. Recent trends in high-energy materials. *Progress in energy and*  
14  
15 *combustion science*, 24:1-30.  
16
- 17 [4] Badgajar, D. M., M. B. Talawar, S. N. Asthana, and P. P. Mahulikar. 2008. Advances  
18  
19 in science and technology of modern energetic materials: An overview. *Journal of Hazardous*  
20  
21 *Materials*, 151:289-305.  
22
- 23 [5] Sikder, A. K., and N. Sikder. 2004. A review of advanced high performance,  
24  
25 insensitive and thermally stable energetic materials emerging for military and space  
26  
27 applications. *Journal of Hazardous Materials*, A112:1-15.  
28
- 29 [6] Gaur, B., B. Lochab, V. Choudhary, and I. K. Varma. 2003. Azido polymers-energetic  
30  
31 binders for solid rocket propellants. *Journal of Macromolecular Science, Part C- Polymer*  
32  
33 *Reviews*, C43(4):505- 545.  
34
- 35 [7] Korobeinichev, O.P., L.V.Kuibida, E. N. Volkov, and A. G. Shmakov. 2002. Mass  
36  
37 spectrometric study of combustion and thermal decomposition of GAP. *Combustion and*  
38  
39 *Flame*, 129(1-2):136-150.  
40
- 41 [8] Sahu, S.K., S. P. Panda, D. S. Sadafule, C. G. Kumbhar, S. G. Kulkarni, and J. V.  
42  
43 Thakur. 1998. Thermal and photodegradation of glycidyl azide polymers. *Polymer*  
44  
45 *Degradation and Stability*, 62:495-500.  
46
- 47 [9] You, J. S., and S. T. Noh. 2013. Rheological and thermal properties of glycidyl azide  
48  
49 polyol-based energetic thermoplastic polyurethane elastomers. *Polym. Int.*, 62:158-164.  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3 [10] Manu, S. K., V. Sekkar, K. J. Scariah, T. L. Varghese, and S. J. Mathew. 2008.  
4  
5 Kinetics of glycidyl azide polymer-based urethane network formation. *Appl. Polym.*  
6  
7 *Sci*110:908-914.  
8
- 9  
10 [11] Eroğlu, M. S., and O. Güven. 1996. Thermal decomposition of poly(glycidyl azide) as  
11  
12 studied by high-temperature FTIR and thermogravimetry. *Journal of Applied Polymer*  
13  
14 *Science*, 61:201-206.  
15
- 16 [12] Selim, K., S. ÖZkar, and L. Yilmaz. 2000. Thermal characterization of glycidyl azide  
17  
18 polymer (GAP) and GAP-based binders for composite propellants. *Journal of Applied*  
19  
20 *Polymer Science*, 77:538-546.  
21
- 22 [13] Sahu, S. K., S. P. Panda, D. S. Sadafule, C. G. Kumbhar, S. G. Kulkarni, and J. V.  
23  
24 Thakur. 1998. Thermal and photodegradation of glycidyl azide polymers. *Polymer*  
25  
26 *Degradation and Stability*, 62:495-500.  
27
- 28 [14] Menke, K., J. Bohnlein-Mauß, and H. Schubert. 1996. Characteristic properties of AN  
29  
30 / GAP-Propellants. *Propellants, Explosives, Pyrotechnics*, 21:139-145.  
31
- 32 [15] Sun, Y., and S. Li. 2008. The effect of nitrate esters on the thermal decomposition  
33  
34 mechanism of GAP. *Journal of Hazardous Materials*, 154:112-117.  
35  
36
- 37 [16] Fazlıoğlu, H., and J. Hacaloğlu. 2002. Thermal decomposition of glycidyl azide  
38  
39 polymer by direct insertion probe mass spectrometry. *Journal of Analytical and Applied*  
40  
41 *Pyrolysis*, 63:327-338.  
42
- 43 [17] Wang, T., S. Li, B. Yang, C. Huang, and Y. J. Li. 2007. Thermal decomposition of  
44  
45 glycidyl azide polymer studied by synchrotron photoionization mass spectrometry. *Phys.*  
46  
47 *Chem. B*, 111:2449-2455.  
48
- 49 [18] Arisawa, H., and T. B. Brill. 1998. Thermal decomposition of energetic materials 71:  
50  
51 Structure- decomposition and kinetic relationships in flash pyrolysis of glycidyl azide  
52  
53 polymer (GAP). *Combustion and Flame*, 112:533-544.  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3 [19] Feng, H. T., K. J. Mintz, R. A. Augsten, and D. E. G. Jones. 1998. Thermal analysis of  
4 branched GAP. *Thermochimica Acta*, 311:105-111.  
5  
6  
7 [20] Tamura G., M. Tanabe, and T. Kuwahara. 2012. Decomposition of GAP single  
8 droplets used as liquid monopropellants. *Propellants Explosives and Pyrotechnics*, 37:302-  
9 307.  
10  
11  
12 [21] Tang, C. J., Y. Lee, and T. A. Litzinger. 1999. Simultaneous temperature and species  
13 measurements of the glycidyl azide polymer (GAP) propellant during laser-induced  
14 decomposition. *Combustion and Flame*, 117:244-256.  
15  
16  
17 [22] Laviolette, M., and M. Auger. 1999. Monitoring the aging dynamics of glycidyl azide  
18 polyurethane by NMR relaxation times. *Macromolecules*, 32:1602-1610.  
19  
20  
21 [23] Vandenburg, E. J. (Hercules Inc.). 1972. U.S. Patent 3,645,917.  
22  
23  
24 [24] Frankel, M. B., L. R. Grant, and J. E. Flanagan. 1992. Historical development of  
25 glycidyl azide polymer *Journal of Propulsion and Power*, 8(3):560-563.  
26  
27  
28 [25] Jutier, J-J., A. De Gunzburg, and R. E. Prud'Homme. 1999. Synthesis and  
29 characterization of poly(3,3 bis(azidomethyl)oxetane-co- $\epsilon$ -caprolactone)s. *Journal of*  
30 *Polymer Science: Part A: Polymer Chemistry*, 37:1027-1039.  
31  
32  
33 [26] Zhai, J., R. Yang, and J. Li. 2008. Catalytic thermal decomposition and combustion of  
34 composite BAMO-THF propellants. *Combustion and Flame*, 154:473-477.  
35  
36  
37 [27] Luo, Y., P. Chen, F-Q. Zhao, R-Z. Hu, S-W. Li, and Y. Gao. 2004. Kinetics and  
38 mechanism of the thermal decomposition reaction of 3,3-  
39 bis(azidomethyl)oxetane/tetrahydrofuran copolymer. *Chinese Journal of Chemistry*, 22:1219-  
40 1224.  
41  
42  
43 [28] Zhang, Y., J. Zhao, P. Yang, S. He, and H. Huang. 2012. Synthesis and  
44 characterization of Energetic GAP-*b*-PAEMA block copolymer. *Polym. Eng. Sci.*, 52:768-  
45 773.  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3 [29] Pisharath, S., and H. G. Ang. 2007. Synthesis and thermal decomposition of  
4 GAP/Poly(BAMO) copolymer. *Polymer Degradation and Stability*, 92:1365-1377.  
5  
6  
7 [30] Barbieri, U., G. Polacco, and R. Massimi. 2006. Synthesis of energetic polyethers  
8 from halogenated precursors. *Macromolecular Symposia*, 234(1):51-58.  
9  
10  
11 [31] Kawamoto, A. M., U. Barbieri, T. Keicher, H. Krause, J. A. S. Holanda, M. Kaiser,  
12 and G. Polacco. 2008. Synthesis and characterization of glycidyl azide-r-(3,3-  
13 bis(azidomethyl)oxetane) copolymers. *Propellant Explosives and Pyrotechnics*, 33:365-372.  
14  
15  
16 [32] Barbieri, U., T. Keicher, R. Massimi, and G. Polacco. 2009. Preliminary  
17 Characterization of Propellants Based on GA/BAMO and pAMMO binders. *Propellant*  
18 *Explosives and Pyrotechnics*, 34(5):427-435.  
19  
20  
21 [33] Kawamoto, A. M., M. F. Diniz, V. L. Lourenço, M. F. K. Takahashi, T. Keicher, H.  
22 Krause, K. Menke, and P. B. J. Kempa. 2010. Synthesis and characterization of GAP/BAMO  
23 copolymers applied at high energetic composite propellants. *Aerosp. Technol. Manag.*,  
24 2(3):307-322.  
25  
26  
27 [34] Barbieri, U., G. Polacco, E. Paesano, and R. Massimi. 2006. Low risk synthesis of  
28 energetic poly(3-azidomethyl-3-methyloxetane) from tosylate precursors. *Propellant*  
29 *Explosives and Pyrotechnics*, 31(5):369-375.  
30  
31  
32 [35] Barbieri, U., T. Keicher, and G. Polacco. 2009. Homo and copolymers of 3-  
33 tosyloxymethyl-3-methyl oxetane (TMMO) as precursors of energetic azide polymers. *e-*  
34 *Polymers*, 9(1):565-575.  
35  
36  
37 [36] Manser, G. E., R. W. Fletcher, and G. C. Shaw. 1983. High Energy Binders. Contract  
38 No. N00014-82-C-0800, Morton Thiokol, Inc. Project JM101.  
39  
40  
41 [37] Hardenstine, K. E., G. V. S. Henderson Jr, L. H. Sperling, C. J. Murphy, and G. E.  
42 Manser. 1985. Crystallization behavior of poly(3,3-bisethoxymethyl oxetane) and poly(3,3-  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 bisazidomethyl oxetane)Journal of Polymer Science: Polymer Physics Edition, 23(8):1597-  
4  
5 1609.

6  
7 [38] Jones, R. B., C. J. Murphy, L. H. Sperling, M. Farber, S. P. Harris, and G. E. Manser.  
8  
9 1985. Thermal decomposition behavior of poly[3,3-bis(ethoxymethyl) oxetane] and related  
10  
11 polyethers. Journal of Applied Polymer Science, 30(1):95-109.

12  
13 [39] Bouchékif, H., M. I. Philbin, M. E. Colclough, and A. J. Amass. 2008. Cationic ring-  
14  
15 opening polymerization of oxetane via a non-steady-state controlled polymerization process: a  
16  
17 comparison of initiators yielding living and nonliving polymers. Macromolecules, 41:1989-  
18  
19 1995.

20  
21 [40] Frankel, M. B., E. F. Witucki, and D.O. Woolery. 1983. U.S. Patent 4,379,894.

22  
23 [41] Wagner, R. I. 1991. U.S. Patent 5,055,600.

24  
25 [42] Cappello, M., P. Lamia, C. Mura, G. Polacco, and S. Filippi. 2015. Azidated ether-  
26  
27 butadiene-ether block copolymers as binders for solid propellants. Journal of Energetic  
28  
29 Materials, submitted.

30  
31 [43] Wilson, E. ., M. B. Frankel, U. S. Patent 4,781,861.

32  
33 [44] Vasudevan, V., and G. Sundararajan 1999. Synthesis of GAP-PB-GAP triblock  
34  
35 copolymer and application as modifier in AP/HTPB composite propellant. Propellants,  
36  
37 Explosives, Pyrotechnics, 24:295-300.

38  
39 [45] Nair, J. K., R. S. Satpute, B. G. Polke, T. Mukundan, S. N. Asthana, and Haridwar  
40  
41 Singh. 2002. Synthesis and characterisation of bis-azido methyl oxetane and its polymer and  
42  
43 copolymer with tetrahydrofuran. Defence Science Journal, 52(2):147-156.

44  
45 [46] Nakabayashi, N., E. Masuhara, Y. Iwakura. 1966. Some reactions of the glycidyl  
46  
47 esters of sulfonic acids. Bulletin of the Chemical Society of Japan, 39:413-417.

48  
49 [47] Kazemi, F., A. R. Massah, M. Javaherian. 2007. Chemoselective and scalable  
50  
51 preparation of alkyl tosylates under solvent-free conditions. Tetrahedron, 63:5083-5087.  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 [48] Reshmia, S., K. P. Vijayalakshmi, Deepthi Thomas, B. K. George, and C. P.  
4  
5 Reghunadhan Nair. 2013. Thermal decomposition of a diazido ester: Pyrolysis GC–MS and  
6  
7 DFT study. Journal of Analytical and Applied Pyrolysis, 104:603-608.  
8  
9  
10

### 11 **Figure captions**

12 Figure 1 - Synthesis and azidation of GAP and PAMMO.  
13

14 Figure 2 – FTIR spectra of monomers, precursors and azidated polymers.  
15

16 Figure 3 – H-NMR spectra of the mesylate monomers and polymers.  
17

18 Figure 4 – GPC curve of PGT (a) and the resultant fitting obtained by deconvolution into two  
19  
20 peaks corresponding to polymer and oligomers (b).  
21  
22

23 Figure 5 – FT-IR spectra of PGM during azidation at 85 °C.  
24

25 Figure 6 - Comparison between  $x_N$  and  $x_M$  for PGM azidation at 85 °C.  
26

27 Figure 7 –  $x_M$  for PTMMO azidation at different temperatures: ○ 85 °C; □ 105 °C; ◇ 125 °C.  
28

29 Solid lines represent the curves calculated with eq. (8).  
30  
31

32 Figure 8 – TGA curves of the synthesized polymers.  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60



Table 1. Azidation reactions of polyether precursors: exiting group, reaction medium and operating temperatures, as reported in literature.

Exiting group	medium	Temperature (°C)	reference
Tosyl, Br	DMSO, DMF	95, 120, 150	[34]
Cl, Br	DMF	90-95	[30]
Cl	DMF	120	[29]
Cl, Br	DMSO	95	[31]
Tosyl, Br	DMSO	120	[35]
Cl, Br	DMSO	120	[33]
Cl	DMSO	100	[8]
Cl	DMF	100	[11]
Cl	DMSO	105	[25]
Cl	DMF	120	[28]
Cl	DMSO	100	[13]
Cl	DMSO	90-95	[24]
Cl	Water	95	[40]
Cl	tetrabutyl ammonium azide (molten salt)	105	[41]
NO <sub>2</sub>	DMSO	100	[43]
Cl	DMSO	105	[44]
Cl	Water	95-100	[45]

Table 2 – Molecular weights of the polymeric precursors calculated by GPC analysis.

Polymer	Mn	Mw	PD	Xn	Oligomer Xn	Oligomer content (w%)
PGT	2300	3200	1.4	14	683	10
PGM	2150	3380	1.6	22	500	3
PTMMO	2400	6650	2.8	26	450	6
PMMMO	3000	5900	2.0	33	700	9

Table 3 - Comparison between the kinetic constants evaluated by using the azide (N), tosyl (Ts) and mesyl (Ms) signals in the FT-IR spectra.

polymer	T	PGM		PGT		T	PMMMO		PTMMO	
group	(°C)	N	Ms	N	Ts	(°C)	N	Ms	N	Ts
k' (s <sup>-1</sup> )	75	0.041	0.0457	0.1168	0.1334	85	0.0313	0.03321	0.046	0.0445
	85	0.118	0.1064	0.1807	0.1933	105	0.17445	0.14741	0.15097	0.14771
	95	0.172	0.1747	0.2727	0.3288	125	0.49413	0.41202	0.31482	0.35203
A (s <sup>-1</sup> )		2.4*10 <sup>8</sup>	4.3*10 <sup>7</sup>	3.4*10 <sup>4</sup>	1.1*10 <sup>4</sup>		5.2*10 <sup>8</sup>	4.7*10 <sup>7</sup>	1.8*10 <sup>5</sup>	6.8*10 <sup>5</sup>
Ea (KJ/mol K)		76.6	71.5	47.9	45.1		82.0	74.8	57.1	61.4

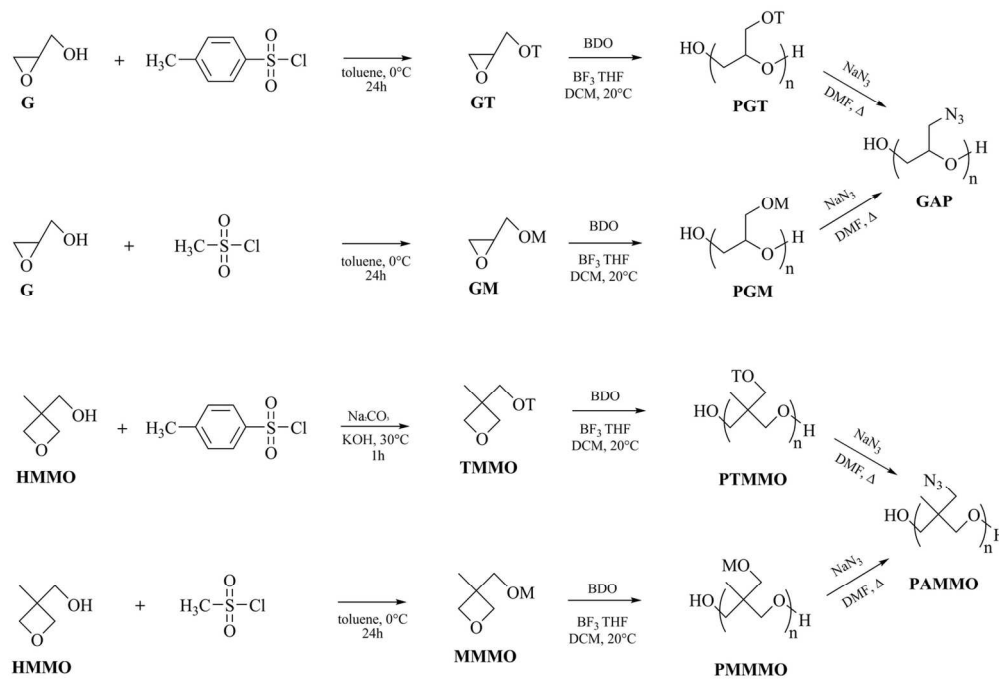


Figure 1 - Synthesis and azidation of GAP and PAMMO.  
136x92mm (300 x 300 DPI)

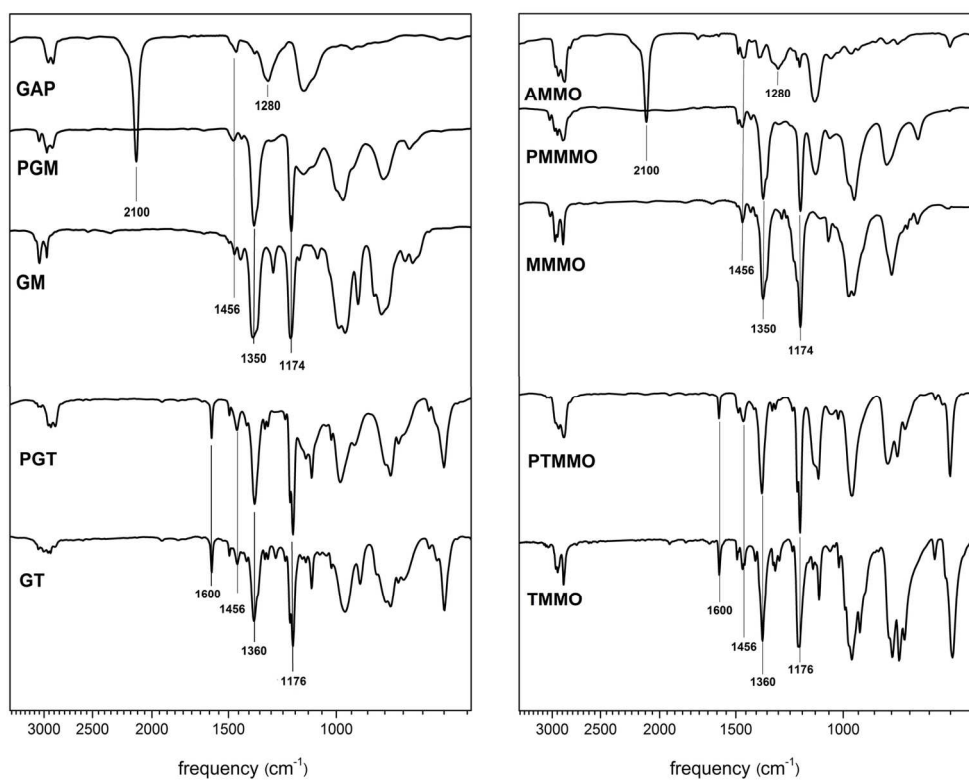


Figure 2 - FTIR spectra of monomers, precursors and azidated polymers.  
151x121mm (300 x 300 DPI)

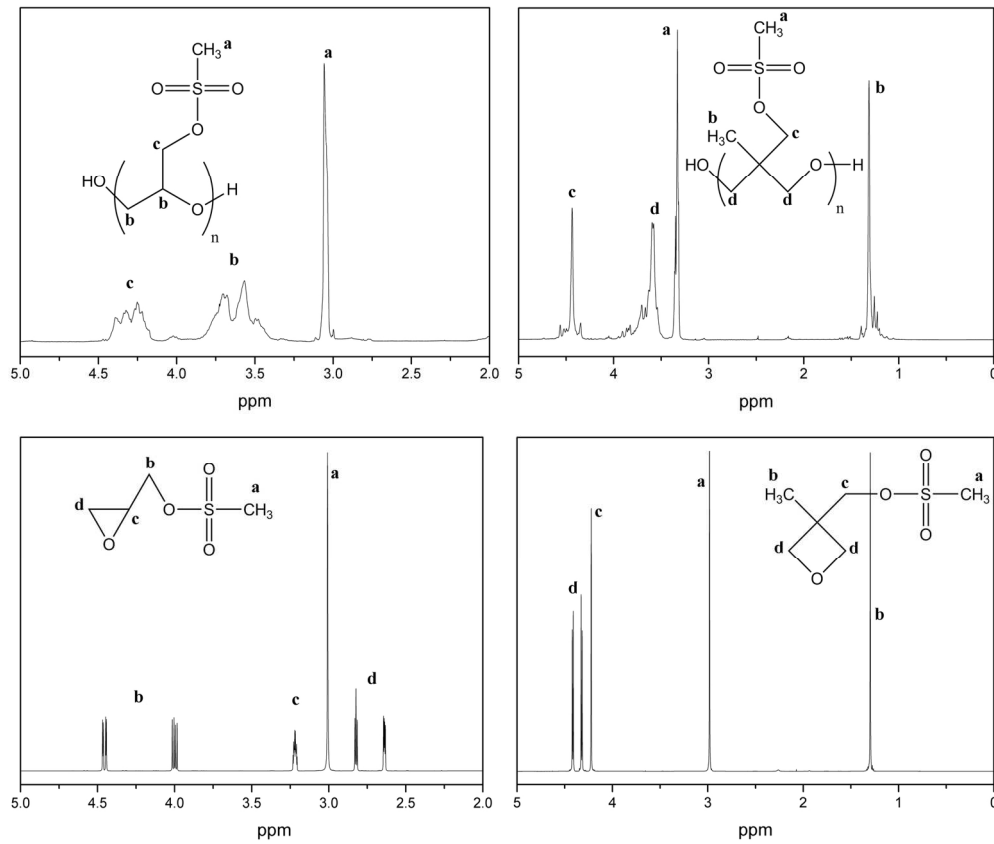


Figure 3 –  $^1\text{H-NMR}$  spectra of the mesylate monomers and polymers.  
165x142mm (300 x 300 DPI)

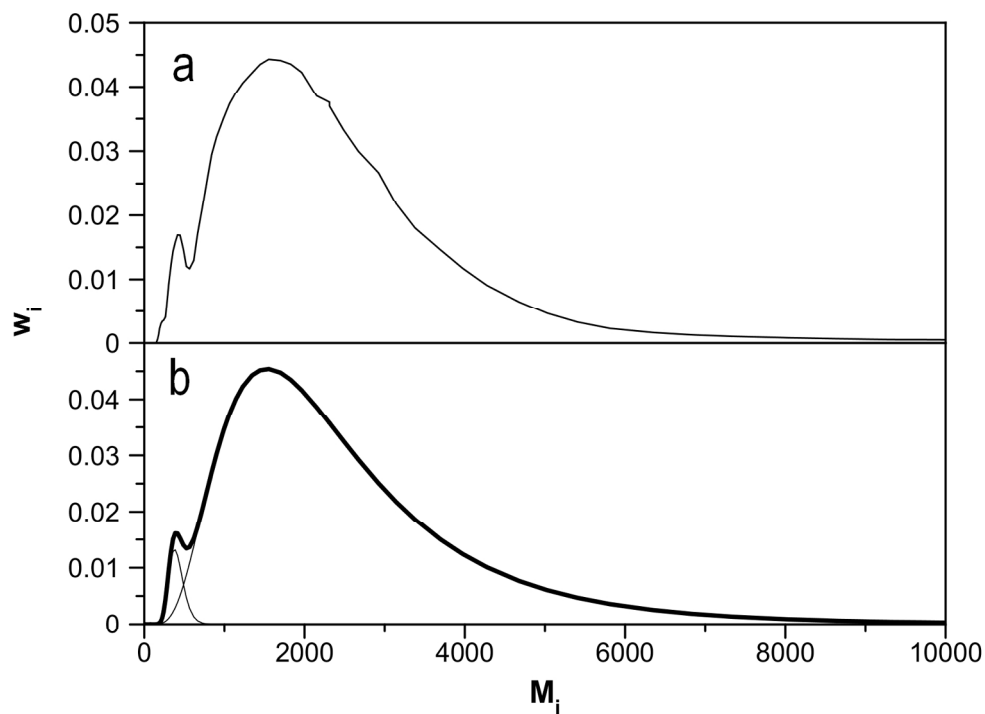


Figure 4 – GPC curve of PGT (a) and the resultant fitting obtained by deconvolution into two peaks corresponding to polymer and oligomers (b).  
666x499mm (72 x 72 DPI)

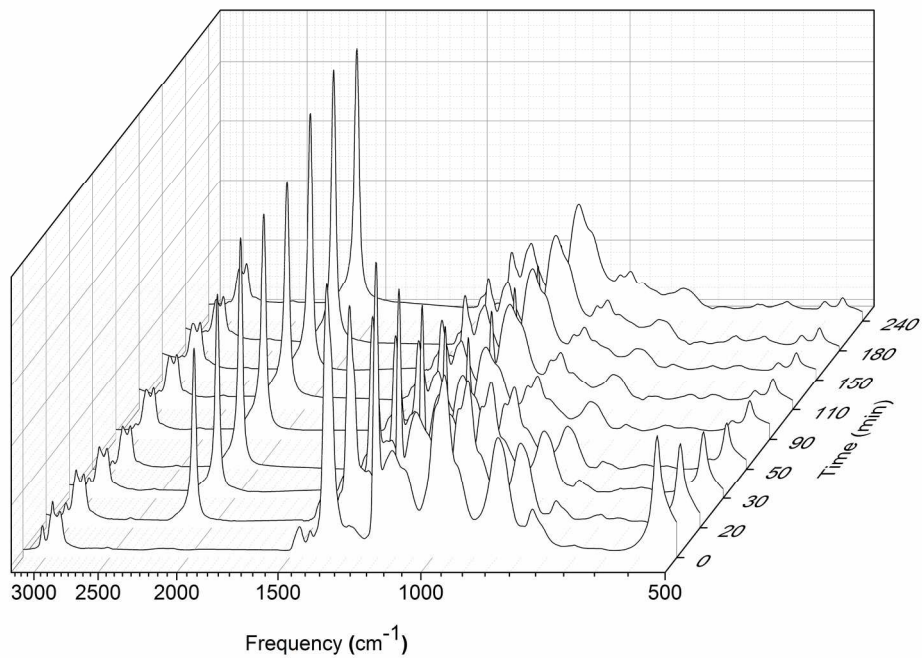


Figure 5 – FT-IR spectra of PGM during azidation at 85 °C.  
199x139mm (300 x 300 DPI)



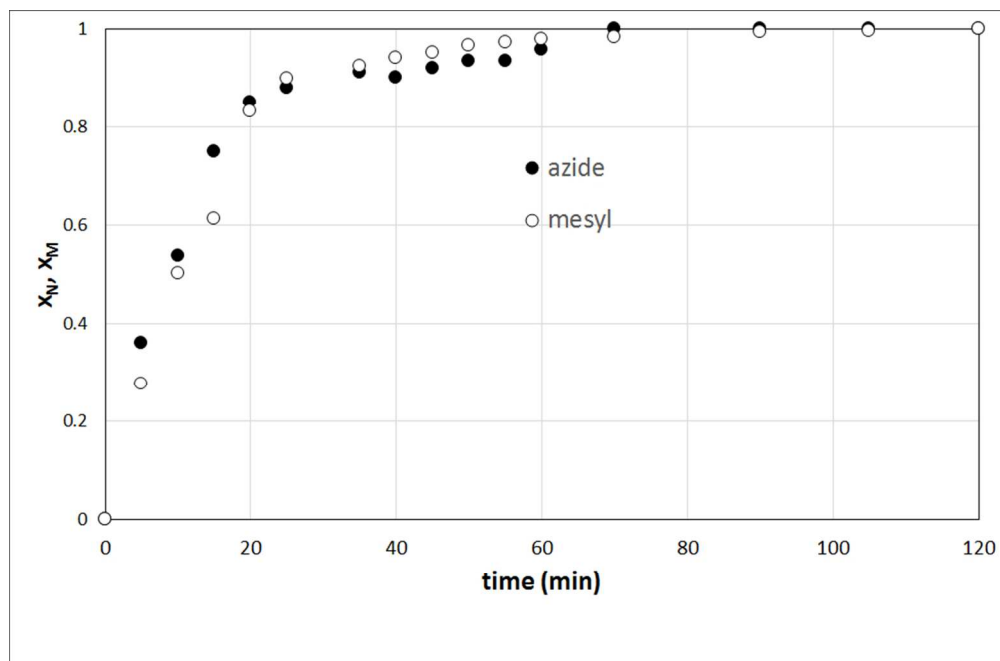


Figure 6 - Comparison between  $x_N$  and  $x_M$  for PGM azidation at 85 °C.

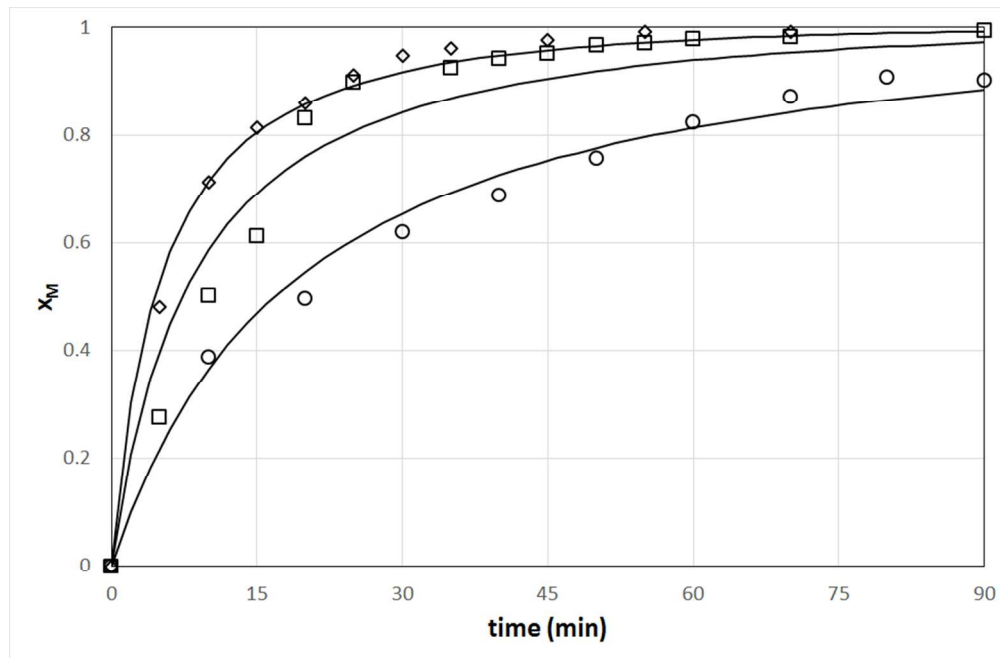


Figure 7 -  $x_T$  for PTMMO azidation at different temperatures:  $\circ$  85 °C;  $\square$  105 °C;  $\diamond$  125 °C. Solid lines represent the curves calculated with eq. (8).

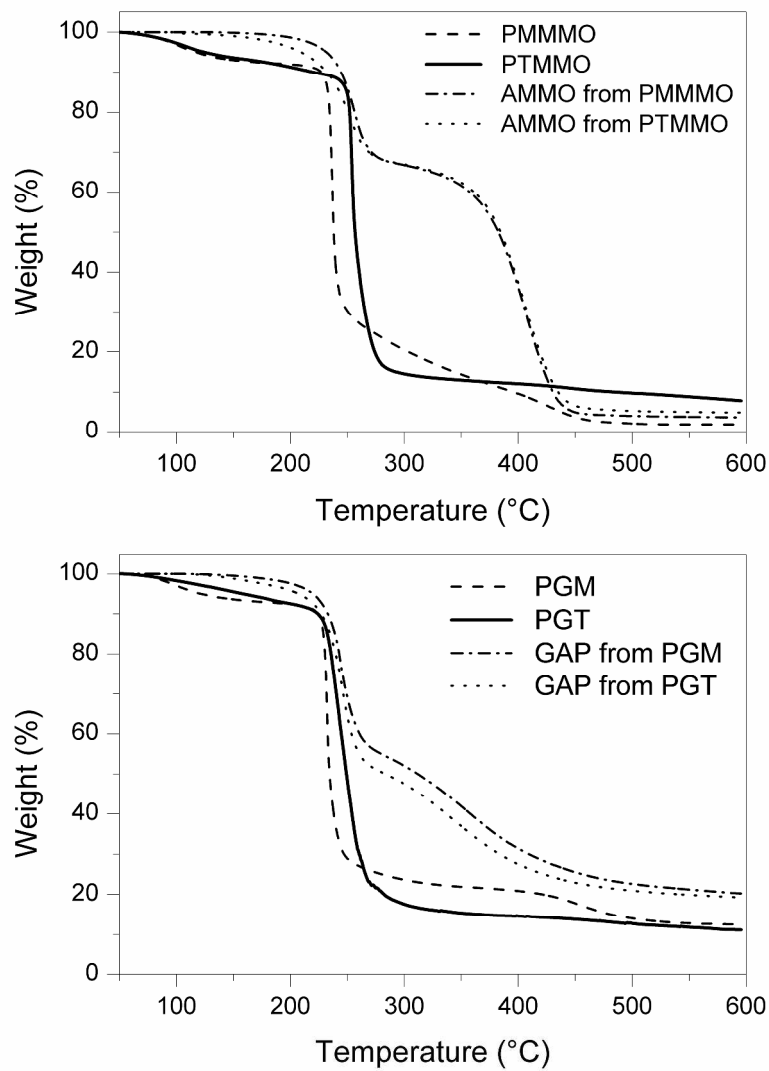


Figure 8 – TGA curves of the synthesized polymers.  
426x612mm (300 x 300 DPI)